

CONTRACTOR OF THE PARTY OF THE

Krasnobrodzka 5; 03-214 Warszawa POLAND

tel.: +48 22 6701181, +48 22 6190733 fax: +48 22 6185938

#### www.continentaltrade.com.pl

# INFORMATION SHEET


office@continentaltrade.com.pl

# **Soda Lime Float Glass (Clear & Tinted)**

Soda lime glass is the most prevalent type of glass. Soda lime glass is prepared by melting the raw materials, such as soda, lime, silica, alumina, and small quantities of fining agents in a glass furnace at temperatures locally up to 1675°C. Soda lime sheet glass is made by floating molten glass on a bed of molten tin. This method gives the sheet uniform thickness and very flat surfaces. Soda lime glass is the base material for most clear, colored and patterned glass types. Due to the high thermal expansion coefficient has a low resistance to sudden changes in temperature.

#### Composition

SiO <sub>2</sub>	72.60%
Na <sub>2</sub> O	13.90%
CaO	8.40%
MgO	3.90%
$Al_2O_3$	1.10%
K <sub>2</sub> O	0.60%
SO <sub>3</sub>	0.20%
Fe <sub>2</sub> O <sub>3</sub>	0.11%

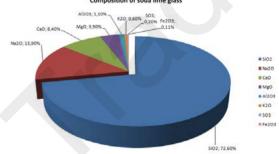

# Flexural strength


Annealed	41 MPa
Heat-Strengthened	83 Mpa
Toughened	165 MPa


# **Properties**

Density (@ 18 °C)		2 500 kg/m <sup>3</sup>
Mohs hardness		5 - 6
Modulus of elastic	city (Young's)	72 GPa
Modulus of Rigidit	cy (Shear)	30 GPa
Bulk Modulus		43 GPa
Poisson's ratio		0.23
Coefficient of ther	mal stress	0.62 MPa/°C
Thermal conductiv	vity	0.937 W/(m K)
Specific heat		0.88 kJ/(kg K)
Coefficient of lines	ar expansion	8.3 * 10 <sup>-6</sup> °C
Refractive Index (S	Sodium D line)	1.523
(1 μm)		1.511
(2 μm)		1.499
Softening point		715 °C
Annealing point		548 °C
Strain Point		514 °C
Emissivity (Hemisp	oherical) at 75°F	0.84
Max. working tem	perature:	
	- not toughened	110 °C
	- toughened	150 °C
Thermal shock Δ:		
	- not toughened	50 °C
	- toughened	118 °C

## **Compressive strength**

Annealed	19 MPa
Heat-Strengthened	39 Mpa
Toughened	77 MPa

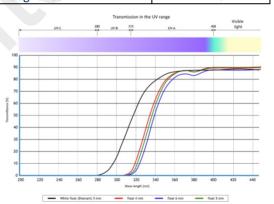



#### **Features**

- Can be chemically strengthened to increase mechanical strength
- Can be heat strengthened or heat tempered to increase thermal shock resistance and mechanical strength
- Can be machined, optically coated, chemically etched, sandblasted, colored, or laminated
- Good flatness and surface quality due to float process
- Economically priced